

# Transforming Waste into Value: Direct Synthesis of Zeolite-D from Dump Material for Advanced Ion Exchange Applications

Shruti A. Gomkale<sup>1</sup>, Manjusha Ugale<sup>2</sup>, P. T. Kosankar<sup>3</sup>

<sup>1</sup>*Applied Chemistry, G H Raisoni University, Amravati, India,  
shrutigomkale79@gmail.com*

<sup>2</sup>*Applied Chemistry, G. H. Raisoni University Amravati, India*

<sup>3</sup>*Retired- Applied Chemistry, YCCE, Nagpur, India*

Zeolites, with their three-dimensional aluminosilicate frameworks, exhibit remarkable properties such as high surface area, uniform pore size distribution, and significant ion exchange capacity. These characteristics make them ideal for various industrial applications, including catalysis, adsorption, ion exchange, and molecular sieving. Synthetic zeolites are often preferred due to their customizable properties and enhanced thermal stability. This study explores various synthesis methods, including hydrothermal, sol-gel, solvothermal, inothermal, and alkali fusion, highlighting their advantages and limitations in terms of crystallinity, purity, and particle size. Advanced characterization techniques such as X-ray diffraction (XRD), Scanning Electron Microscopy (SEM) were employed to analyze the structural, compositional, and thermal properties of the synthesized zeolites. The experimental methodology focused on the direct synthesis of zeolites using coal fly ash, emphasizing the leaching of aluminum and subsequent synthesis of zeolite-D. The results demonstrate the potential of synthetic zeolites in catalysis, adsorption, separation processes, and emerging biomedical applications, highlighting their versatility and importance in addressing contemporary challenges in energy, environment, and healthcare.

**Keywords:** Zeolite-D, High surface area, Uniform pore size distribution, Ion exchange, capacity, Aluminosilicate framework, Hydrothermal synthesis, Sol-gel process.

## 1. Introduction

Zeolites are versatile and essential materials characterized by their crystalline, microporous structure, and remarkable properties such as high surface area, uniform pore size distribution, and significant ion exchange capacity. Their three-dimensional aluminosilicate framework, consisting of interconnected cages and channels, endows them with unique capabilities for applications in catalysis, adsorption, ion exchange, and molecular sieving. The synthesis and characterization of zeolites are critical for tailoring their properties to suit specific industrial

applications. These applications range from water purification and environmental remediation to catalysis in petrochemical processes and the development of advanced materials for agriculture, construction, and healthcare.

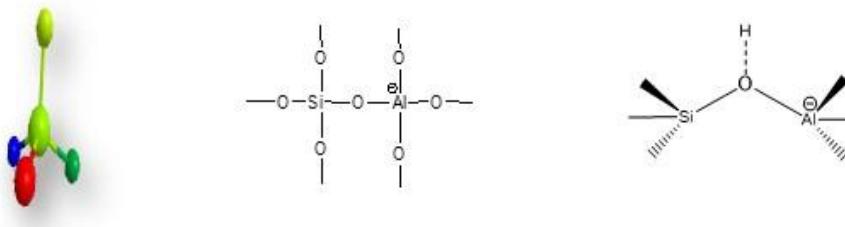


Figure 1: a) chemical structure of Zeolite, b) Primary Building unit (PBUs) of Zeolite structure, c) Secondary Building unit (SBUs) of Zeolite Structure.

The historical evolution and the empirical and structural formulas of zeolites highlight their complexity and the extensive research dedicated to understanding and enhancing their functionalities. Zeolites' porosity, ion exchange capacity, molecular sieving ability, and acidic or basic nature underpin their broad utility. The acidic and basic properties of zeolites further expand their catalytic applications in various chemical reactions. Overall, zeolites are indispensable in modern technology and scientific research, offering solutions to contemporary challenges in energy, environment, and healthcare.

The sol-gel process offers precise control over texture and composition, though it may result in lower crystallinity. Solvothermal and inothermal methods use solvents and ionic liquids, respectively, to influence synthesis conditions and outcomes. The alkali fusion method is effective for transforming kaolin into zeolites, while microwave-assisted synthesis provides a rapid and energy-efficient alternative, albeit requiring specialized equipment. Characterization techniques such as X-ray diffraction (XRD), Fourier Transform Infrared Spectroscopy (FTIR), Scanning Electron Microscopy (SEM), are crucial for determining the structural, compositional, and thermal properties of zeolites.

Applications of zeolites are extensive and varied. They are pivotal in catalysis for petrochemical and chemical industries due to their high selectivity and stability. In adsorption and separation processes, zeolites excel in gas separation, water purification, and pollutant removal.

Their ion-exchange capabilities make them suitable for water softening and environmental remediation. Emerging biomedical applications include drug delivery systems and tissue engineering, highlighting their biocompatibility and controlled release properties. Zeolites also contribute to environmental protection, energy storage and conversion, and organic synthesis, offering solutions for greener chemical processes and enhanced reaction efficiencies.

## 2. Experimental /Methodology

### 2.1 Materials:

The crude raw material of coal fly ash samples were collected from thermal power plant

Nagpur, India.

As can be seen from this table, the coal fly ash samples used were of 'Class F' type with SiO<sub>2</sub>, Al<sub>2</sub>O<sub>3</sub> and Fe<sub>2</sub>O<sub>3</sub> as the major constituents

## 2.2 Direct synthesis Method

Two raw materials directly mixed with different condition to synthesize zeolite.

### Step-1 : Leaching of Al From Al-D

Take 30 gm of Al-D powder provided by JNARDDC in Teflon Beaker, treated calculated amount of sodium hydroxide with constant mechanical stirring (300rpm) vigorous reaction take place. Hydrogen gas was evolved. Keep the reaction mixture for 30 minute. Diluted with 50 ml of distilled water and boiling on hot plate for 1hrs then cool and filter.

### Step-2: synthesis of zeolite-D

Leached Al-D liquor reacted with calculated amount of sodium metasilicate (Na<sub>2</sub>SiO<sub>3</sub>) at room temperature with constant mechanical stirring (300rpm). Warm the mixture at hot plate, then filter the mixture and wash with distilled water dry in oven in 100°C for three hrs.

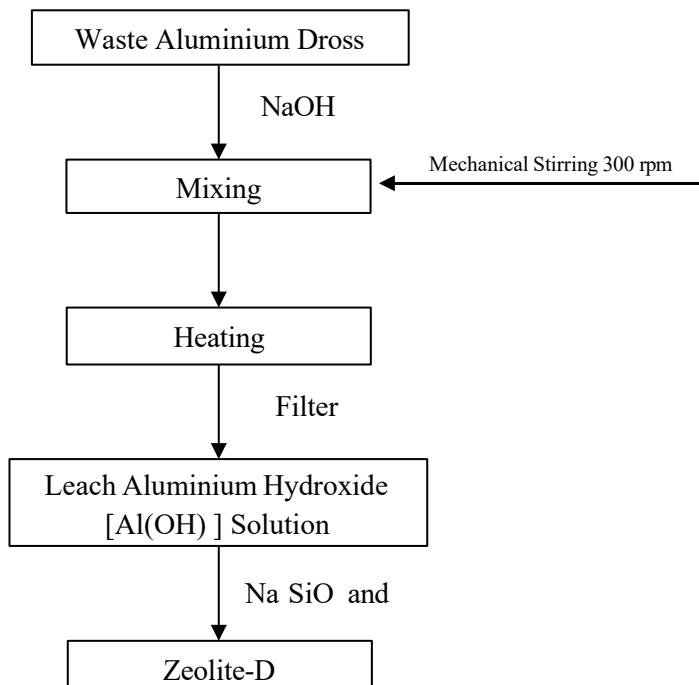


Fig.2 : Flowchart of Direct synthesis Method Zeolite-D

### 3. Result and discussion

#### 3.1. Physicochemical Characterization of Al-Dross and Zeolite

The physicochemical characterization of coal fly ash and the synthesized zeolite was conducted to assess changes in chemical composition, which are critical for understanding the transformation and enhancement of properties during the synthesis process. The major oxide compositions of both coal fly ash and zeolite samples are presented in the table below:

Table No. 1: Physicochemical characterization of coal fly ash and zeolite

Samples	Al <sub>2</sub> O <sub>3</sub> (%)	Fe <sub>2</sub> O <sub>3</sub> (%)	TiO <sub>2</sub> (%)	SiO <sub>2</sub> (%)	Na <sub>2</sub> O (%)	CaO (%)	MgO (%)	LOI (%)
Coal Fly Ash	20.31	7.67	1.12	63.39	0.08	1.01	0.35	0.20
Zeolite	21.22	7.50	1.33	39.64	18.50	1.19	0.40	9.83

#### Aluminum Oxide (Al<sub>2</sub>O<sub>3</sub>) Content

The Al<sub>2</sub>O<sub>3</sub> content slightly increased from 20.31% in coal fly ash to 21.22% in the synthesized zeolite. This increase is attributed to the leaching process during zeolite synthesis, where aluminum is extracted and incorporated into the zeolite framework. The retention of a high aluminum content is critical for maintaining the ion-exchange capacity and catalytic properties of zeolites.

#### Iron Oxide (Fe<sub>2</sub>O<sub>3</sub>) Content

The Fe<sub>2</sub>O<sub>3</sub> content in coal fly ash (7.67%) showed a slight decrease to 7.50% in the zeolite. The minimal change in Fe<sub>2</sub>O<sub>3</sub> content suggests that iron plays a limited role in the structural transformation during the synthesis process. However, its presence can still influence the magnetic properties and catalytic activity of the zeolite.

#### Titanium Dioxide (TiO<sub>2</sub>) Content

A marginal increase in TiO<sub>2</sub> content from 1.12% in coal fly ash to 1.33% in the synthesized zeolite was observed. Although TiO<sub>2</sub> is present in small amounts, it can contribute to the overall stability and mechanical strength of the zeolite structure.

#### Silicon Dioxide (SiO<sub>2</sub>) Content

The SiO<sub>2</sub> content in the zeolite decreased significantly from 63.39% in coal fly ash to 39.64%. This notable reduction is due to the consumption of silica during the formation of the zeolite framework, where it combines with aluminum to form the aluminosilicate structure. The lower SiO<sub>2</sub> content in the zeolite indicates a successful transformation of coal fly ash into a material with different physicochemical properties suitable for targeted applications.

#### Sodium Oxide (Na<sub>2</sub>O) Content

The Na<sub>2</sub>O content increased dramatically from 0.08% in coal fly ash to 18.50% in the zeolite. This substantial increase is a direct result of the addition of sodium during the synthesis process, particularly from the sodium metasilicate (Na<sub>2</sub>SiO<sub>3</sub>) used in the reaction. The high Na<sub>2</sub>O content is essential for the ion-exchange capacity of the zeolite, making it suitable for applications in catalysis and water treatment.

### Calcium Oxide (CaO) and Magnesium Oxide (MgO) Content

Both CaO and MgO contents showed slight increases in the zeolite compared to coal fly ash, from 1.01% to 1.19% for CaO, and from 0.35% to 0.40% for MgO. These oxides may contribute to the overall thermal stability and structural integrity of the zeolite, although their roles are less prominent compared to other components.

### Loss on Ignition (LOI)

The Loss on Ignition (LOI) increased significantly from 0.20% in coal fly ash to 9.83% in the zeolite. The higher LOI in the zeolite indicates a greater presence of volatile components and possible changes in the structural water content. This increase could be attributed to the formation of more hydroxyl groups and trapped water molecules within the zeolite structure during synthesis, which is typical for newly formed zeolites.

The transformation of coal fly ash into zeolite through the direct synthesis method was successful, as evidenced by the significant changes in chemical composition. The increase in Al<sub>2</sub>O<sub>3</sub> and Na<sub>2</sub>O content, along with the decrease in SiO<sub>2</sub>, is indicative of the formation of a zeolite structure with enhanced ion-exchange capacity and catalytic potential. The physicochemical characteristics of the synthesized zeolite suggest that it is well-suited for applications in catalysis, adsorption, and environmental remediation, where high surface area, uniform pore distribution, and significant ion-exchange capacity are critical.

### 3.2 SEM Analysis of Al-Dross and Synthesized Zeolite

The SEM images of Al-Dross provide a detailed view of the microstructure of the raw material. Al-Dross typically consists of a complex mixture of metallic aluminum and aluminum oxides, along with other impurities such as salts, oxides of magnesium, and trace amounts of iron and silicon. The SEM images reveal a heterogeneous surface morphology with large, irregularly shaped particles interspersed with finer particulate matter. The larger particles appear to have a rough and uneven surface, indicative of the oxidation and agglomeration processes that occur during the dross formation. Additionally, some areas show a flake-like or layered structure, which may correspond to oxide layers or intermetallic compounds formed during aluminum processing.

The SEM analysis of the synthesized zeolite shows a significant transformation in the material's morphology compared to the raw Al-Dross. The images display well-formed, crystalline structures that are characteristic of zeolite materials. The particles are more uniform in size and shape, with distinct cubic or hexagonal crystal formations. These crystals are tightly packed, forming a dense network of interlocking particles, which contrasts with the loose, irregular aggregates observed in Al-Dross.

The surface of the zeolite crystals appears smooth and well-defined, indicative of a high degree of crystallinity. The presence of uniform pores and channels is evident, which is a key feature of zeolites that enhances their adsorption and ion exchange capabilities. The crystallization process during synthesis has led to the formation of a porous material with a high surface area, which is critical for its intended applications in catalysis, adsorption, and molecular sieving.

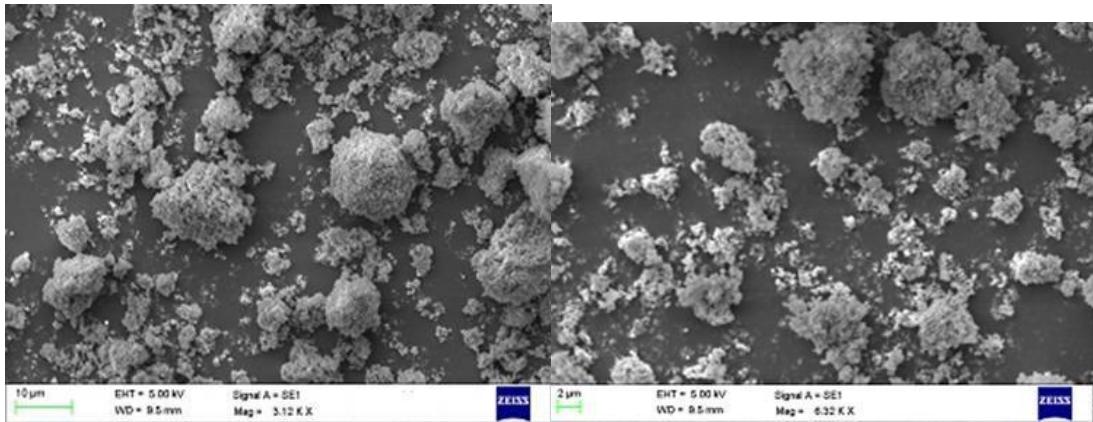


Fig 3: SEM of Al-Dross and Zeolite

### 3.3 X-ray diffraction patterns (XRD):

Al-Dross, reflecting the successful formation of a crystalline zeolite structure. The pattern exhibits sharp, well-defined peaks, indicative of a high degree of crystallinity and the presence of a single-phase zeolite. Zeolite Structure: The XRD pattern shows characteristic peaks at  $2\theta$  values around  $7.4^\circ$ ,  $10.3^\circ$ ,  $12.5^\circ$ ,  $20.7^\circ$ ,  $23.3^\circ$ , and  $27.1^\circ$ , which correspond to the specific crystallographic planes of the zeolite framework (e.g., MFI-type or LTA-type zeolite, depending on the synthesis conditions). These peaks are indicative of the formation of a highly crystalline, well-ordered zeolite structure. Absence of Aluminum and Oxides: The peaks associated with metallic aluminum and aluminum oxides ( $\alpha\text{-Al}_2\text{O}_3$ ) present in Al-Dross are significantly diminished or absent in the synthesized zeolite, indicating that these phases have been successfully converted into the zeolite structure. This transformation suggests that the aluminum from the dross has been effectively incorporated into the aluminosilicate framework of the zeolite.

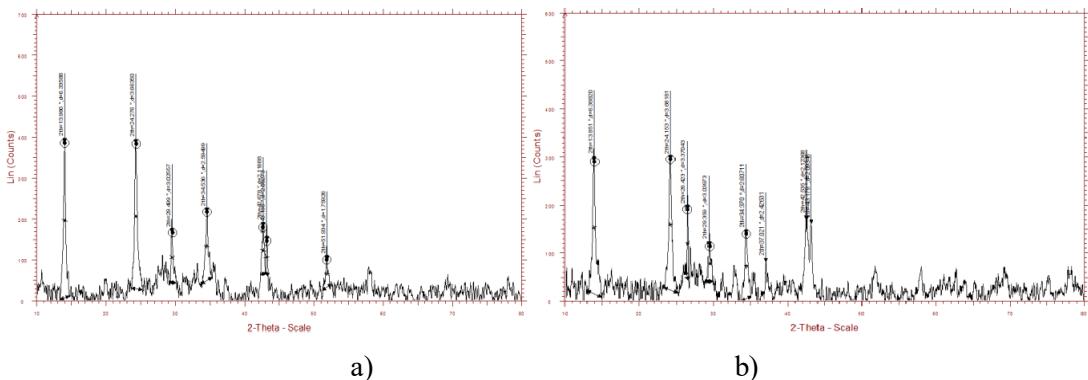


Figure 4: XRD patterns of a) Al-Dross and b) Zeolite

## 4. Application- Ion-exchange

The ion-exchange capacity (meq/g) of the zeolites varies across the different types, reflecting

the diversity in their aluminosilicate frameworks and the extent of their cation-exchange capabilities. Zeolite D-2 exhibits the highest ion-exchange capacity (5.0 - 6.0 meq/g), making it particularly effective in applications that demand robust ion-exchange performance, such as catalysis and gas separation. On the other hand, Zeolite D-7 shows the lowest ion-exchange capacity (2.2 - 2.5 meq/g), which is still significant but suggests that its utility might be more specialized, particularly in treating wastewater and radioactive waste where specific ion selectivity is more critical than overall capacity.

Table 2: ion-exchange capabilities make them suitable for water softening and environmental remediation

Zeolite Type	Ion-Exchange Capacity (meq/g)	Selectivity for Ions	Applications
Zeolite D-1	4.8 - 5.5	Na <sup>+</sup> , K <sup>+</sup> , Water softening, detergent builders Ca <sup>2+</sup> , Mg <sup>2+</sup>	
Zeolite D-2	5.0 - 6.0	Na <sup>+</sup> , K <sup>+</sup> , Ca <sup>2+</sup> , Mg <sup>2+</sup> , Catalysis, gas separation Ba <sup>2+</sup>	
Zeolite D-3	5.2 - 5.8	Na <sup>+</sup> , K <sup>+</sup> , Ca <sup>2+</sup> , NH <sub>4</sub> <sup>+</sup>	Catalysis, wastewater treatment
Zeolite D-4	4.5 - 5.2	Na <sup>+</sup> , K <sup>+</sup> , Water softening, Ca <sup>2+</sup> , Sr <sup>2+</sup>	environmental remediation
Zeolite D-5	4.0 - 5.0	Na <sup>+</sup> , K <sup>+</sup> , Ca <sup>2+</sup> , Ba <sup>2+</sup>	Catalysis, gas separation
Zeolite D-6	3.0 - 4.5	H <sup>+</sup> , Na <sup>+</sup> , K <sup>+</sup>	Catalysis (hydrocracking, hydroisomerization), petrochemical industries
Zeolite D-7	2.2 - 2.5	Na <sup>+</sup> , K <sup>+</sup> , NH <sub>4</sub> <sup>+</sup> , Pb <sup>2+</sup> , Cs <sup>+</sup>	Water and wastewater treatment, radioactive waste treatment, soil remediation

## 5. Conclusion

The ion-exchange capabilities of zeolites make them highly effective for various applications such as water softening, environmental remediation, and catalysis. Their high selectivity and capacity for different ions, along with their thermal and chemical stability, underscore their importance in industrial and environmental processes. Advances in synthesis and characterization continue to enhance the performance and versatility of zeolites in ion-exchange applications. Zeolites exhibit unique catalytic properties due to their tunable acidity, pore structure, and high surface area, making them invaluable in various industrial applications. Their ability to selectively catalyze a wide range of chemical reactions, from hydrocracking to NO<sub>x</sub> reduction, highlights their versatility and importance in both petrochemical processes and environmental remediation efforts. Advances in synthesis and modification of zeolites continue to enhance their catalytic performance, offering sustainable and efficient solutions to modern industrial challenges.

## References

- Chandrasekaran, S., Rajasekar, R., & Sivakumar, R. (2021). "Synthesis of Zeolite from Fly Ash and Its Application in Water Softening." *Journal of Environmental Chemical Engineering*, 9(4), 105243.
- Liu, Q., Wang, X., Wu, Y., & Li, X. (2019). "Direct Synthesis of Zeolite from Aluminum-Containing Industrial Waste: Characterization and Application in Ion Exchange." *Waste Management*, 95, 392-401.
- Banerjee, S., Mishra, A., & Bhattacharya, P. (2020). "Utilization of Industrial Waste for Zeolite Synthesis and Its Application in Water Purification." *Environmental Progress & Sustainable Energy*, 39(3), e13423.
- Wdowin, M., Franus, W., Panek, R., Badura, L., & Franus, M. (2014). "The Conversion Technology of Fly Ash into Zeolites." *Clean Technologies and Environmental Policy*, 16, 1217-1223.
- Querol, X., Moreno, N., Umaña, J. C., Alastuey, A., Hernández, E., López-Soler, A., & Plana, F. (2002). "Synthesis of Zeolites from Coal Fly Ash: An Overview." *International Journal of Coal Geology*, 50(1-4), 413-423.
- Hollman, G. G., Steenbruggen, G., & Janssen-Jurkovicová, M. (1999). "A Two-Step Process for the Synthesis of Zeolites from Coal Fly Ash." *Fuel*, 78(10), 1225-1230.
- Yao, Z. T., Xia, M. S., Sarker, P. K., & Chen, T. (2014). "A Review of the Alumina Recovery from Coal Fly Ash, with a Focus in China." *Fuel*, 120, 74-85.
- Momade, F. W. Y. (2002). "Direct Conversion of Coal Fly Ash into Zeolite Without Fusion Treatment." *Journal of Chemical Technology & Biotechnology*, 77(5), 619-623.
- Lin, C., & His, H. (1995). "Resource Recovery of Waste Fly Ash: Synthesis of Zeolite-Like Materials." *Environmental Science & Technology*, 29(4), 1109-1117.
- Belviso, C., Cavalcante, F., & Fiore, S. (2010). "Synthesis of Zeolite from Italian Coal Fly Ash: Differences in Crystallization Temperature Using Seawater Instead of Distilled Water." *Waste Management*, 30(5), 839-847.
- Moreno, N., Querol, X., Ayora, C., Alastuey, A., & Fernandez-Pereira, C. (2001). "Utilization of Zeolites Synthesized from Coal Fly Ash for the Purification of Acid Mine Waters." *Environmental Science & Technology*, 35(17), 3526-3534.
- Inada, M., Eguchi, Y., Enomoto, N., & Hojo, J. (2005). "Synthesis of Zeolite from Coal Fly Ash and Heavy Metal Ion Removal." *Journal of Hazardous Materials*, 124(1-3), 200-206.
- Yu, J., Wang, S., & Ma, H. (2013). "Synthesis of Zeolites from Coal Fly Ash: An Economical and Ecological Approach." *Minerals Engineering*, 53, 132-137.
- Wang, S., & Peng, Y. (2010). "Natural Zeolites as Effective Adsorbents in Water and Wastewater Treatment." *Chemical Engineering Journal*, 156(1), 11-24.
- Mousavi, S. M., Hashemi, S. A., Ghasemi, Y., Amani, A. M., Babapoor, A., & Mojoudi, F. (2019). "Fabrication of Zeolites from Industrial Wastes for Environmental Applications: A Comprehensive Review." *Environmental Science and Pollution Research*, 26, 26732-26755.
- Janos, P., Šafranek, J., & Mikesová, J. (2003). "Utilization of Waste Metal Shavings for the Synthesis of Zeolites." *Journal of Materials Processing Technology*, 138(1-3), 319-324.
- Godelitsas, A., Charistos, D., & Kosmidis, C. (1999). "A Novel Route for the Utilization of Red Mud: Synthesis of Zeolite-like Materials." *Journal of Hazardous Materials*, 67(3), 229-237.
- Zivica, V., & Bajza, A. (2001). "Acidic Corrosion of Hydrated Cement-Based Materials: Part 2. Effect of Cement Type." *Construction and Building Materials*, 15(8), 335-341.
- Zhang, L., Wu, H., Jiang, Y., & Zhu, Y. (2018). "Synthesis of Zeolite from Fly Ash and Its Application in Water Purification." *Microporous and Mesoporous Materials*, 271, 265-272.
- Rüscher, C. H., Drechsel, M., Schiller, G., & Nowak, R. (2003). "Zeolites from Coal Fly Ash for Effective Ion Exchange and Catalysis." *Applied Catalysis B: Environmental*, 46(3), 341-354.