

Durability Analysis And Mechanical Performances Of Sand Concrete Modified With Carbon Nanotubes

Zina Mansouri^{1 2}, Hachem Chaib^{1 2}, Ali Kechired¹

¹Department of Civil Engineering and Hydraulics, University Kasdi Merbah Ouargla, Ouargla 30000, Algeria.

²Laboratory of Exploitation and Valorization of Natural Resources in Arid Zones, Ouargla 30000, Algeria

* Corresponding e-mail address: chaib.hachem.dz@gmail.com

Received 19/08/2024

Accepted 24/10/2024

Published 28/10/2024

This work involves studying the evolution of durability of sand concrete containing two mineral additives (crushed dune sand and carbon nanotubes (CNTs)) in four storage media (free surface, plastic film, tap water and groundwater). The potential negative effects of adding these alternative materials can be reduced by adding very small amounts of carbon nanotubes to the cement system. This study investigates the feasibility of using these alternative materials and carbon nanotubes (CNTs) in the production of lightweight concrete. The first step of our research was to characterize the ingredients used to produce sand concrete. Then, we studied the addition of 2% carbon nanotubes (CNTs) and dune sand powder from the Ouargla area (5%, 10%) as well as the combination of the two additions (2% CNT + 5% SDP; 2% CNT + 10% SDP). Flexural tensile and compressive strength tests were carried out after 7, 28, 90 and 120 days to be able to estimate and evaluate the durability.

The results obtained in this experimental study allow us to say that sand concrete with 5SDP 2 CNT or 10SDP 2 CNT has a stable compressive strength after 90 days in tap water and groundwater. These sand concretes show a positive improvement in strength at all times in the storage medium "plastic film".

Keywords: durability, sand concrete, mineral additions, crushed dune sand, carbon nanotubes(CNT), preservation media, strength.

Introduction

The durability of reinforced concrete structures is a very important factor in the field of civil or industrial engineering, because the alterations of concrete are varied; they reach either the cement matrix or the reinforcements, and sometimes both. The origins of these alterations are numerous, including: the placing, the mechanical strength of the concrete at 28 days, the cracks formed under the effect of the stresses applied to the structure and the aggressive agents of the external environment.

Algeria, especially the south, is rich in natural materials, which can be used directly in the construction field. Their properties should be studied in order to extend their use. Among these materials, which can be exploited, and which we are going to study, sand of dune is available in great quantity and the studies of the valorization of this material is inexistent in the field of construction, and we also add in this study the silica smoke. The main objective of this study is to make a contribution to the evaluation of the effects of mineral additions such as crushed dune sand and carbon nanotubes(CNT)on the durability of sand concrete.

Methods and materials

Construction sand

The construction sand used is from Djamaa -El Oued located 211 km north of Ouargla. The following table and curve represent the results of the different tests on the sand.

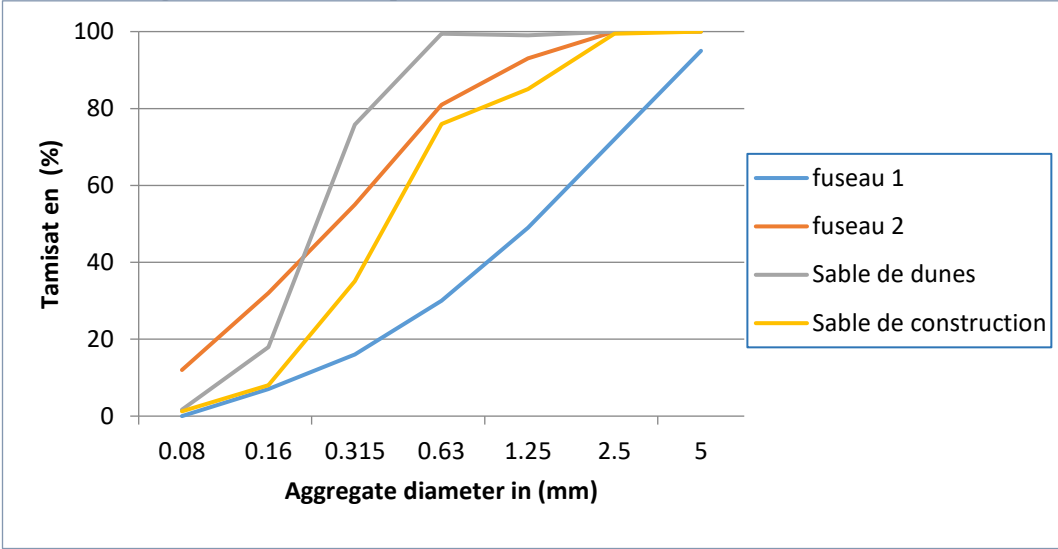


Figure 1. Trigonometrical curve of the sand of Djamaa -El Oued.

Physical characteristics of the construction sand used

Table 1. Characteristics of building sand

M _f	M _{app} (g/cm ³)	M _{abs} (g/cm ³)	ES _v (%)	ES _p (%)	F (%)	C _u	C _c
2.08	1.65	2.54	71.14	73.43	1.99	3.15	1.96

Crushed dune sand

Sand is a product of the slow disintegration of rocks under the action of erosive agents such as air, rain, etc. This material is found in large quantities in the Saharan regions. Dune sand has long been used in the execution of embankment works, foundations and road works.

We used a dune sand from Sidi Khouild Ouargla, which is a fine golden sand whose maximum dimension of the large grains is 2mm. We used the sand in the form of powder through a crusher of the university OUARGLA and sieving with a sieve of diameter 0.08mm.



Figure 2. The crushing stages of dune sand.

- Apparent density: 0.960 g/cm³.
- Absolute density: 2.55 g/cm³.
- Blaine's specific surface: 5304 cm²/g.

The chemical analysis of the powdered dune sand which is carried out at LTPS Ouargla is represented in the table below:

Table 2. Chemical analysis of dune sand powder.

	NaCl %	CaSO ₄ %	SO ₃ ⁻² %	SO ₄ ⁻² %	CaCO ₃ %	Insoluble%
SDP	0.418	6.263	1.166	1.400	0.00	102.2

Carbon nanotubes(CNT)

In this study, CNT having 99.5% SiO₂ content, were utilized. The CNT were synthesized in the laboratory of Kasdi Merbah Ouargla University. The properties of NT and CNT are given in Table 3.



Figure 3. Carbon nanotubes(CNT)used.

The chemical analysis of the carbon nanotubes(CNT)which is carried out at LTPS Ouargla is represented in the table below [GUEMMOUDA,K and ZOUZOU,L.2019]:

Table 3. Chemical analysis of silica fume. [GUEMMOUDA,K and ZOUZOU,L.2019]

Properties	OPC	carbon nanotubes
Physical		
Form	Powder	Powder
Specific gravity	3.15	2.2
Bulk unit weight (kg/m ³)	1140	0.8-1.3 g/cm ³
Initial setting time (min)	85	
Final setting time (min)	265	-
Specific area (cm ² /g)	3390	(0.4–0.9) × 103 m ² /g
Particle size (nm)	-	0.2–2 nm
Melting point (°C)	-	1600
Boiling point (°C)	-	2230
Molecular weight (g/mol)	-	60.08
Color	Gray	black
Chemical compositions (%)		
SiO ₂	20.86	99.5
Al ₂ O ₃	6.17	-
Fe ₂ O ₃	3.05	-
CaO	61.89	-
MgO	2.88	-
SO ₃	2.67	-
K ₂ O	0.86	-
Na ₂ O	0.83	-
LOI	0.97	-

The chemical composition of the cement used is shown in the table below:

Table 4. Physical properties of cement.

Normal consistency (%)	Blaine fineness(cm ² /g) (NA231)	Absolute density g/cm ³	Bulk density g/cm ³	Time to set (min)	End of set time (min)
27.5	3454	3.14	1.0374	180	285

Table 5. Chemical analysis of cement [data sheet].

Fire loss (%) (NA5042)	Sulphate content (SO ₃) (%)	Magnesium oxide content MgO (%)	Chloride content (NA5042) (%)
0.5 à 3%	1.8 à 3	1.2 à 3	0.01 à 0.05

Table 6.Compressive strength of cement [data sheet].

2 days (MPa)	28 days (MPa)
≥ 10	≥ 42.5

Compositions used

In our work, we prepared about 144 specimens for the physical and mechanical characterization of sand concrete made with different percentages of carbon nanotubes(CNT)and dune sand powder. The nomenclatures named in the work are given:

- **C**: Cement.
- **SDP**: Powdered dune sand.
- **CNT**: carbon nanotubes
- **E**: Mixing water.
- **SC**: Construction sand.

According to the studies carried out by GUEMOUDA K and ZOUZOU L, the following compositions give the best results in terms of resistance

Table 7. compositions used for sand concrete.

Composition	E/L	C %	SDP %	CNT %
C1	0.48	100	0.0	0.0
C2	0.5	93	5	2
C3	0.5	88	10	2

The following table shows the quantities of the compositions in cubic metres (m³) of sand concrete:

Table 8. The quantities of sand concrete compositions (m³).

Composition	C (kg)	SC (Kg)	E (Kg)	CNT (Kg)	SDP (Kg)
C1	491.07	1473.21	235.71	0	0
C2	454.68	1466.70	244.44	9.78	24.44
C3	430.22	1466.70	244.44	9.78	48.88

Preparation of the specimens

The specimens are prismatic in shape with a square cross-section (40 x 40 x 160) mm. They must be molded as soon as possible after the sand concrete has been made. With the three-cell metal mould and its riser firmly attached to the impact table, the first of two layers of sandcastle is introduced. The layer is spread evenly using the large spatula and then tightened with 60 impacts. The second layer is then introduced, level with the small spatula and clamped again with 60 impacts.

The mould is removed from the impact table, and after the rise has been removed, the excess sandcastle is removed by leveling. The surface of the specimens is then smoothed.



Figure 4. Impact table and specimen moulds (40x40x160) mm.

Specimen storage media

After the demoulding of the specimens after 24 hours, the specimens (40x40x160) mm were stored in the different media "open air, plastic films, tap water, and ground water" for 7, 28, 90 and 120 days.

Results and Interpretations

In this part, the results of the mechanical resistance tests (extramural and compressive), which were carried out on sand concrete in the dry state using the equipment available in the laboratory of the Civil and Hydraulic Engineering Department, are presented and analyses. The following abbreviations were used:

AL: the storage medium of the "free area" specimens.

FP: storage medium for "plastic film" specimens.

ER: the storage medium for "tap water" specimens.

5SDP 2CNT: sand concrete with 5% dune sand powder plus 2% carbon nanotubes(CNT)

10SDP 2CNT: sand concrete with 10% dune sand powder plus 2% carbon nanotubes(CNT)

Table 9. Bending strength results.

Conservation area	Composition	Flexural strength (MPa)			
		7 days	28days	90 days	120days
Free air	M C	6.01	6.95	5.94	5.41
	5SDP 2CNT	5.39	5.86	5.39	5.39
	10SDP 2CNT	4.53	4.61	5.24	4.69
Plastic film	M C	5.24	5.78	6.80	7.11
	5SDP 2CNT	4.45	6.10	6.10	7.26
	10SDP 2CNT	3.44	5.47	5.63	7.34
Flush water	M C	6.95	10.00	9.14	8.44
	5SDP 2CNT	6.25	7.73	7.81	8.67
	10SDP 2CNT	6.09	7.5	8.70	8.70

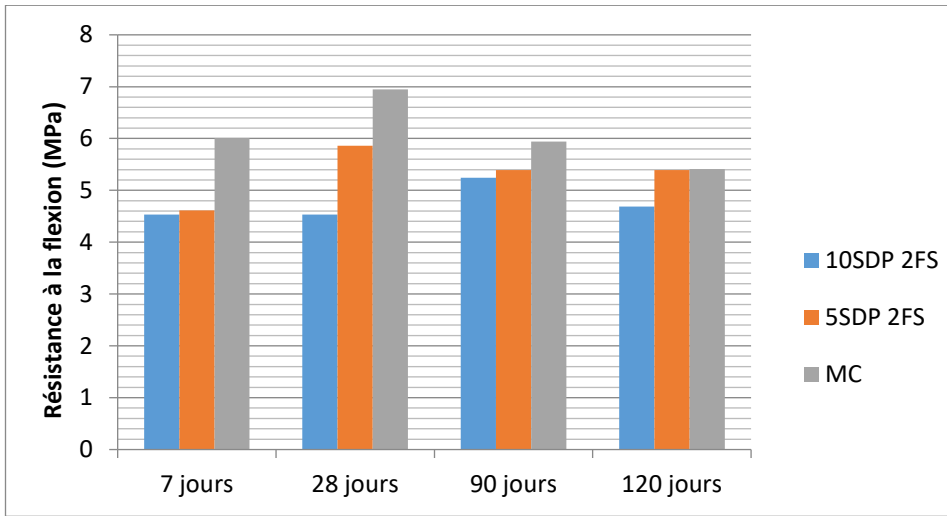


Figure 5. Extramural strength of specimens kept in free area.

From figure 5, we notice that there is a positive evolution of all the sand concretes in the 7 to 28 days, but we notice a drop in stress of the MC and 5SDP 2 CNT after 28 days. Although the 10SDP 2 CNT sandcastle showed an improvement in mechanical strength at 90 days, at 120 days we notice a drop in mechanical strength of all the sandcastles. This may be due to the dryness of the sandcastle due to the temperature rise in July, although the 5SDP2 CNT sandcastle shows a stability in strength.

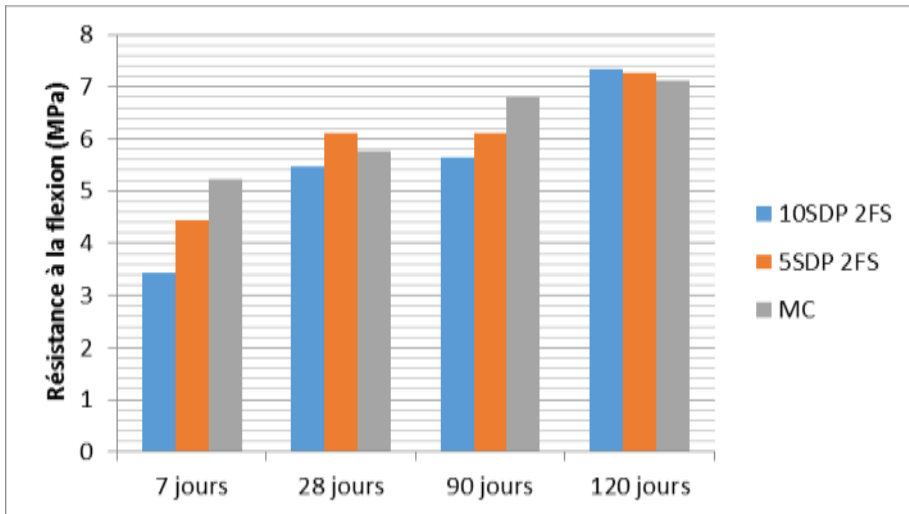


Figure 6. Extramural strength of specimens retained in plastic film.

From Figure 6, we can see that there is a positive stress evolution of all sand castle in the period 7-28 days and 90-120 days. While we observe the stability of strength of sand concrete

with 5SDP 2 CNT and 10SDP 2 CNT in the period 28-90 days, and for the classical sand concrete we notice a positive evolution of the stress in the period 28-90 days.

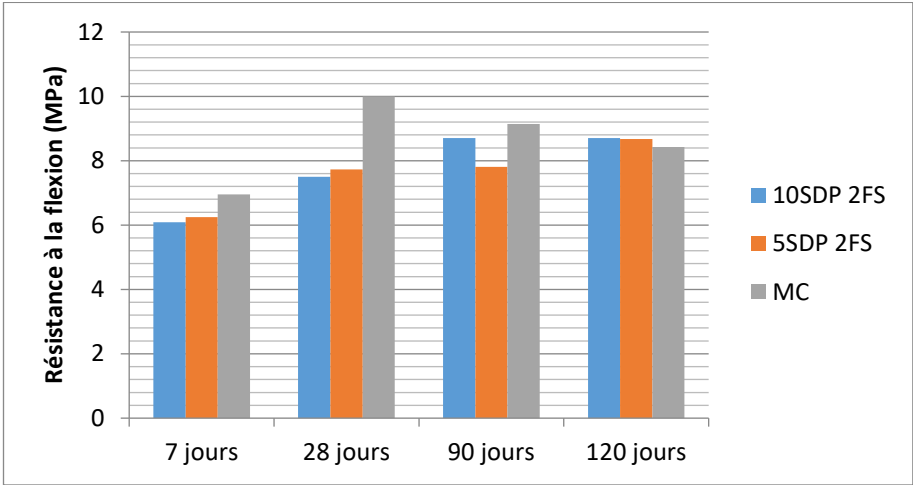


Figure 7. Extramural strength of specimens stored in tap water.

According to figure 7, we notice that there is a positive evolution of mechanical resistance of all the sand concrete in the period of 7-28 days, but after 28 days we observe that there is a fall of constraint for MC on the other hand 5SDP2 CNT presents an improvement of resistance and 10SDP2 CNT presents a stability of mechanical resistance.

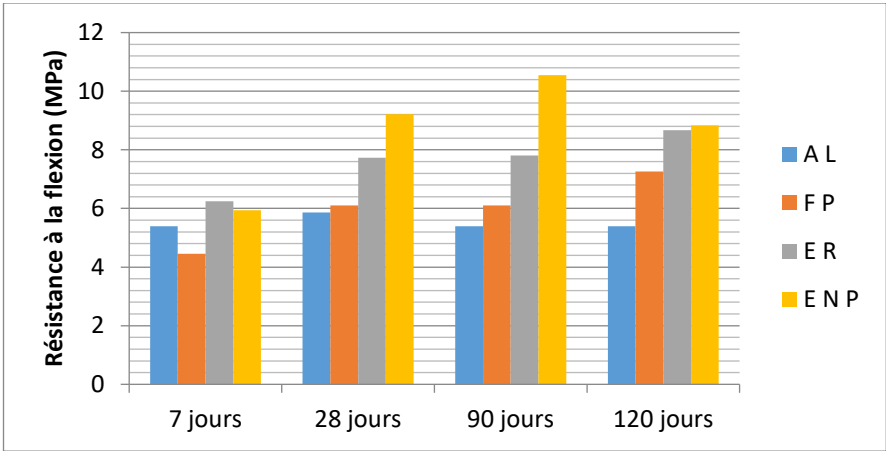


Figure 8. Extramural strength of sandcastle specimens with 5% SDP and 2 CNT in different media.

From figure 8, we notice that the sand concrete specimens with 5% SDP and 2% CNT in the ENP medium at 90 days give the best result from the strength point of view, but there is a drop

in stress after 90 days. While the specimens in E R or F P show a positive evolution of the mechanical strength at all ages. When the specimens in A L give the lowest stress values but they are almost stable after 28 days.

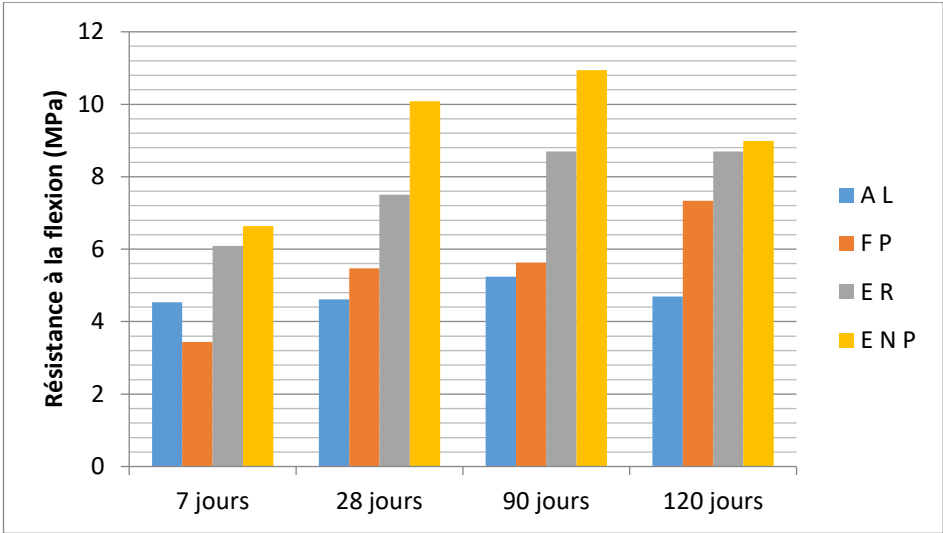


Figure 9. Extramural strength of sand concrete specimens with 10% SDP and 2 CNT at different media.

From Figure 9, we observe that there is a positive evolution of the specimens in ER at the period 7-90 days, after 90 days there is a stabilization of the stress. Although the specimens kept in ENP show the good result compared to the others, we notice a drop in stress at the period 90-120 days. The specimens in the F P storage medium show an improvement in mechanical strength at all ages. It can be seen that the specimens at A L give the lowest stress values.

It can be seen that the conventional sand concrete and the sand concrete with 10SDP 2FS give the best result in extramural strength, but a drop in strength of all sand concretes can be seen, although the sand concretes with 5SDP 2 NS and 10SDP 2 NS show strength stability at 90-120 days.

Table 10. Compressive strength results.

Milieu de conservation	Composition	Compressive strength (MPa)			
		7 days	28 days	90 days	120 days
Free air	M C	21.25	22.06	17.52	16.46
	5SDP 2CNT	16.20	18.91	21.86	23.09
	10SDP 2CNT	16.65	18.33	22.39	17.79
Plastic film	M C	20.51	22.29	15.48	12.70
	5SDP 2CNT	15.31	15.42	20.48	20.65
	10SDP 2CNT	16.29	17.36	18.76	27.89
Flush water	M C	28.50	31.66	32.76	30.90

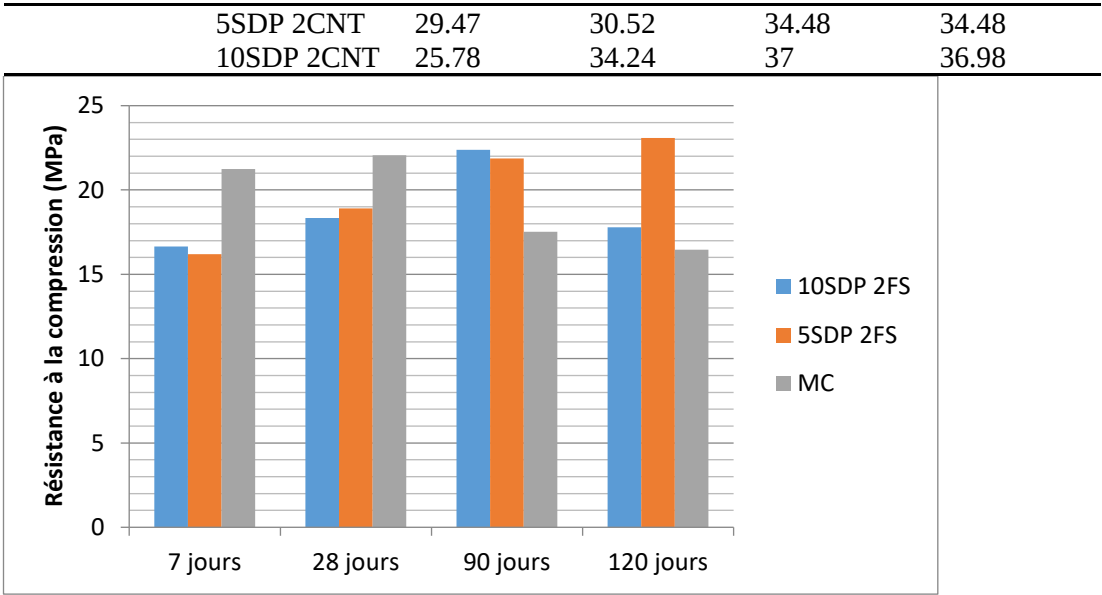


Figure 10. Compressive strength of the specimens kept in free area.

From figure 10, we notice that there is a positive evolution of strength for all the sand concretes at the period 7-28 days, but we notice a drop in stress of the MC after 28 days and we notice a drop in stress of the 10SDP2 CNT sand concrete after 90 days, on the other hand the 5SDP 2CNT sand concrete showed a positive evolution of stress at the period 90-120 days.

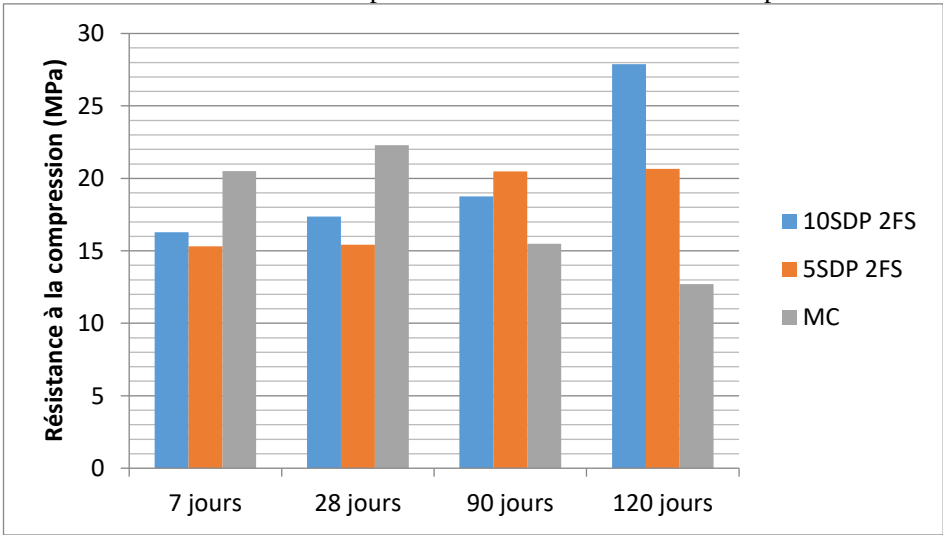


Figure 11. Compressive strength of specimens retained in plastic film.

From figure 11, we notice that the sand concrete with 5% SDP+2% CNT and 10% SDP+2% CNT gives a positive strength evolution at all ages. An improvement in the mechanical strength of M C is noticed, but there is a drop in stress after 28 days.

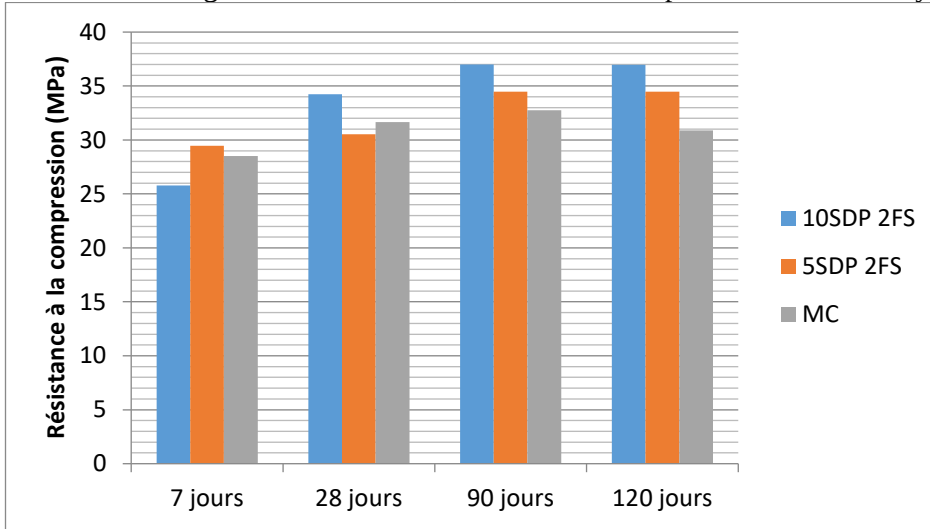


Figure 12. Compressive strength of specimens stored in tap water.

From figure 12, we notice that there is a positive evolution of strength of all the sand concrete at the period 7- 90 days. After 90 days, we notice that there is a drop in MC stress, and for the 5SDP2 CNT and 10SDP2 CNT sand concrete, we observe that there is a stability of stress at this period.

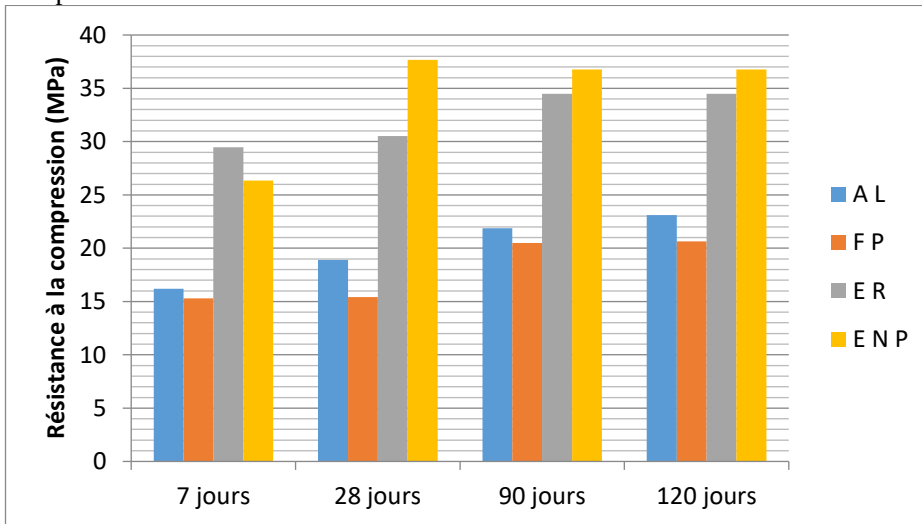


Figure 13. Compressive strength of sand concrete specimens with 5% SDP and 2% CNT at different media.

From figure 13, we observe that the specimens kept in A L, F P, and E R give a positive evolution of the mechanical strength at all ages, except for the specimens in ENP which give an improvement of the strength at 28 days, but we notice a drop in stress after 28 days with a stability of stress at the period 90-120 days. We note that the OE medium gives the best mechanical strength results at all ages.

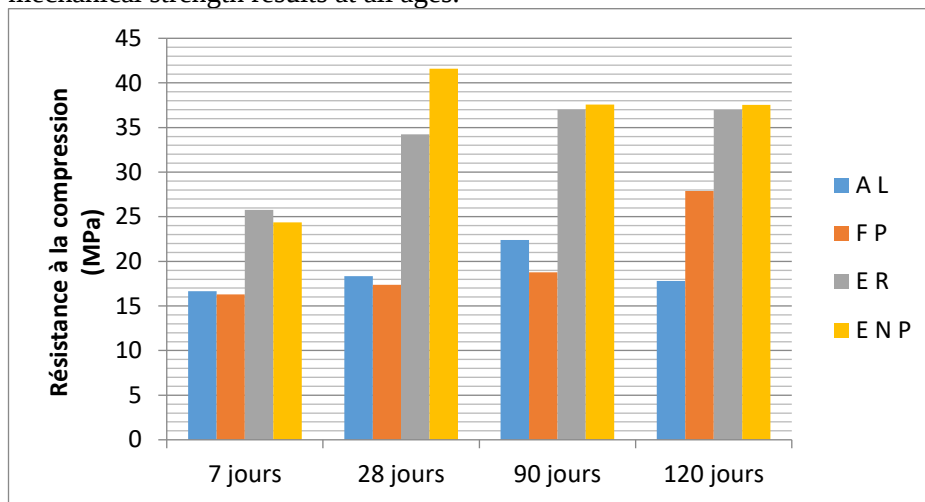


Figure 14. Compressive strength of sand concrete specimens with 10% SDP and 2 CNT at different media.

From Figure 14, we notice that the specimens in FP and ER give a positive evolution of the mechanical strength at all ages with a stable stress for the specimens in ER at the period 90-120 days. Although the specimens in ENP have the highest strength values at 28 days, we observe a drop in stress after 28 days with a stable stress at 90-120 days.

We note that the specimens in AL show an improvement in stress at 7-90 days, but after 90 days there is a drop in strength. We note that the OE medium gives the best strength results at all ages.

Sand concrete with 5SDP 2 CNT or 10SDP 2 CNT has a stable compressive strength after 90 days in the "tap water and groundwater" media. These sand concretes show a positive improvement in strength at all times in the storage medium "plastic film". Conventional sandcastle and sand castle with 10SDP 2 CNT give the best compressive strength result.

Conclusion

This experimental work is a contribution to the improvement of durability of sand concrete by mineral addition, we used four preservative media and two compositions with carbon nanotubes(CNT)and dune sand powder. The objective of this work is to study experimentally the influence of the use of natural products existing in the country on the durability to make a durable locally composed cement. The results obtained in this experimental study allow us to draw the following conclusions:

Sand concrete with 5SDP 2CNT and 10SDP 2 CNT has a strength stability of 90-120 days. The addition of powdered dune sand and carbon nanotubes(CNT)improves the durability of sand concrete. sand concrete stored in the medium (groundwater) shows the best mechanical results compared to other media used. sand concrete stored in the medium (free area) shows the worst mechanical results compared to other media used. In the storage medium (plastic film), sand concrete with 5SDP 2 CNT and 10SDP 2 CNT show a positive evolution of mechanical strength in the long term.

References

- [1] Bederina M, Marmoret L, Mezreb K, Khenfer Mm, Bali A, Quéneudec M. Effectof The Addition Of Wood Shavings On Thermal Conductivity Of Sand Concretes:Experimental Study And Modelling. *Constrbuild Mater* 2007;21:662–8.
- [2] Taфраoui, A., 2009. Contribution A La Valorisation Du Sable De Dune De L'erg Occidental (Algerie). Application Aux Nouveaux Betons. Phd Thesis. University Of Toulouse France
- [3] Bederina M, Laidoudi B, Goullieux A, Khenfer Mm, Bali A, Quéneudec M. Effectof The Treatment Of Wood Shavings On The Physico-Mechanical Characteristicsof Wood Sand Concretes. *Constr Build Mater* 2009;23:1311–5.
- [4] El Euch Khay, S., Neji, J., Loulizi, A., 2010. Shrinkage Properties Of Compacted Sandconcrete Used In Pavements. *Constr. Build. Mater* 24, 1790e1795.
- [5] Guettala, S., Mezghiche, B., 2011. Compressive Strength And Hydration With Age Ofcement Pastes Containing Dune Sand Powder. *Constr. Build. Mater* 25,1263e1269.
- [6] Al-Harthy, A.S., Abdel Halim, M., Taha, R., Al-Jabri, K.S., 2007. The Properties Ofconcrete Made With Fine Dune Sand. *Constr. Build. Mater* 21, 1803e1808.
- [7] Abu Seif, E.S., 2013b. Performance Of Cement Mortar Made With Fine Aggregates Ofdune Sand, Kharga Oasis, Western Desert, Egypt: An Experimental Study. *Jordan J.Civ. Eng.* 7, 270e284.
- [8] C. Meyer, The Greening Of The Concrete Industry, *Cem. Concr. Compos.* 31 (8)(2009) 601–605.
- [9] M. Casuccio, M.C. Torrijos, G. Giaccio, R. Zerbino, Failure Mechanism Ofrecycled Aggregate Concrete, *Constr. Build. Mater.* 22 (7) (2008) 1500–1506
- [10] N. Kachouh, Hilal El-Hassan, Tamer El-Maaddawy Effect Of Steel Fibers On The Performance Of Concrete Made With Recycledconcrete Aggregates And Dune Sand.*Construction And Building Materials* 213 (2019) 348–359
- [11] M.S. De Juan, P.A. Gutiérrez, Study On The Influence Of Attached Mortar Contenton The Properties Of Recycled Concrete Aggregate, *Constr. Build. Mater.* 23 (2)(2009) 872–877.
- [12] F. Debieb, L. Courard, S. Kenai, R. Degeimbre, Mechanical And Durability Properties Of Concrete Using Contaminated Recycled Aggregates, *Cem. Concr.Compos.* 32 (6) (2010) 421–426
- [13] Ö. Çakir, Experimental Analysis Of Properties Of Recycled Coarse Aggregate(Rca) Concrete With Mineral Additives, *Constr. Build. Mater.* 68 (2014) 17–25
- [14] V. Corinaldesi, Mechanical And Elastic Behaviour Of Concretes Made Ofrecycled-Concrete Coarse Aggregates, *Constr. Build. Mater.* 24 (9) (2010)1616–1620.
- [15] M. Malešev, V. Radonjanin, S. Marinković, Recycled Concrete As Aggregate Forstructural Concrete Production, *Sustainability* 2 (5) (2010) 1204.
- [16] S. Ghorbani, S. Sharifi, S. Ghorbani, V.W. Tam, J. De Brito, R. Kurda, Effect Ofcrushed Concrete Waste's Maximum Size As Partial Replacement Of Naturalcoarse Aggregate On The Mechanical And Durability Properties Of Concrete,*Resour. Conserv. Recycl.* 149 (2019) 664–673
- [17] G Calcado L Alves E Vazquez R D Toledo Filho Construction And Demolitionwaste Aggregates: Analysis Of The Physical And Mechanical Properties Ofmortars *Iop Conf. Ser.: Mater. Sci. Eng.* 652 012016 10.1088/1757-899x/652/1/012016

<https://Iopscience:Iop.Org/Article/10.1088/1757> .

- [18] R. L. S. Ferreira, M. A. S. Anjos, C. Maia Et Al., Long-Term Analysis Of The Physical Properties Of The Mixed Recycled Aggregate Andtheir Effect On The Properties Of Mortars, Construction Andbuilding Materials, <https://doi.org/10.1016/j.conbuildmat.2020.121796>
- [19] V. Abreu, L. Evangelista, J. De Brito, The Effect Of Multi-Recycling On Themechanical Performance Of Coarse Recycled Aggregates Concrete, *Constr. Build.Mater.* 188 (2018) 480–489, <https://doi.org/10.1016/j.conbuildmat.2018.07.178>.
- [20] R.L. Da S. Ferreira, M.A.S. Anjos, E.F. Ledesma, J.E.S. Pereira, A.K.C. Nóbrega, Evaluation Of The Physical-Mechanical Properties Of Cement-Lime Basedmasonry Mortars Produced With Mixed Recycled Aggregates, *Mater.Construcción.* 70 (2020) 210. Doi: 10.3989/Mc.2020.02819
- [21] Y.V. Zontov, O.Y. Rodionova, S.V. Kucheryavskiy, A.L. Pomerantsev, Dd-Simca– A Matlab Gui Tool For Data Driven Simca Approach, *Chemometrics Andintelligent Laboratory Systems* 167 (2017) 23–28, <https://doi.org/10.1016/j.chemolab.2017.05.010>
- [22] G. Bai, C. Zhu, C. Liu, B. Liu, An Evaluation Of The Recycled Aggregatecharacteristics And The Recycled Aggregate Concrete Mechanical Properties,*Constr. Build. Mater.* 240 (2020) 117978,<https://doi.org/10.1016/j.conbuildmat.2019.117978>
- [23] J. Silva, J. De Brito, R. Veiga, Incorporation Of Fine Ceramics In Mortars, *Constr.Build. Mater.* 23 (1) (2009) 556–564
- [24] Abdessalammekhermeche ,Hachem Chaib, Abdelouahed Kriker. Influence Of Temperature On The Prototypes Made By Earth Bricks (Raw And Fired) Reinforced With Date Palm Fibers Intended For Constructions In The Saharan Zone (Ouargla). Volume 08, Issue 02, 2021, Pp. 1087-1101 Doi: 10.31838/Jcr.08.02.112
- [25] A. Mardani-Aghabaglou Et Al. Improving The Mechanical And Durability Performance Of Recycledconcrete Aggregate-Bearing Mortar Mixtures By Using Binary And Ternarycementitious Systems/ *Construction And Building Materials* 196 (2019) 295–306
- [26] Hachem Chaib, Abdelouahed Kriker. Contribution To Study Of Influence Of Different Additions On Thermo-Mechanical Properties Of Adobe Based On El Hadjira Clay, *Journal Of Critical Reviews.* Volume 08, Issue 01, 2021, Pp. 1005-1015 Doi: 10.31838/Jcr.08.01.112
- [27] Hachem Chaib, Abdelouahed Kriker. Contribution To The Study Of Influence Of Cement Addition On The Mechanical And Thermal Properties Of Traditional Plaster Bricks. *Solid State Technology.* Volume 63, Issue 05, 2020, Pp. 9380-9390
- [28] S. Jesus Et Al.Rendering Mortars With Incorporation Of Very Fine Aggregates Fromconstruction And Demolition Waste / *Construction And Building Materials* 229 (2019) 116844
- [29] Bouziani, T., Bederina, M., Hadjoudja, M., 2012. Effect Of Dune Sand On The Properties Of Flowing Sand-Concrete (Fsc). *Ijcs* 6, 59e64
- [30] Hachem Chaib, Mohammed Boucherba, Krikerabdelouahed, Study Of The Characteristics Of Mud Bricks Reinforced With Plastic Polymer, *International Journal Of Advanced Research In Engineering And Technology (Ijaret).* Volume 11, Issue 12, December 2020, Pp. 767-778